



## Original Research Article

# Enhanced Photocatalytic Performance of ZnO NPs in the Presence of Solar Light and H<sub>2</sub>O<sub>2</sub> for Degradation of Tetracycline from Wastewater: Optimal Conditions for Green Products

Rafid Tajaldeem<sup>1</sup> , Mohammed B. Alqaraguly<sup>2</sup> , Ola Hamad Salah<sup>3</sup> , Alzahraa S. Abdulwahid<sup>4</sup> , Talib Munshid Hanoon<sup>5</sup>, Zahraa Hamzaa Abud Alzahraa<sup>6</sup> , Alaa A. Omran<sup>7\*</sup> 

<sup>1</sup> Department of Pharmaceutical, Al-Zahraa University for women, Iraq

<sup>2</sup> Medical Laboratories Techniques, Hilla University College, Babylon, Iraq

<sup>3</sup> Department of Medical Laboratories Technology, Al-Manara College for Medical Sciences, Maysan, Iraq

<sup>4</sup> Department of Medical Laboratories Technology, Al-Hadi University College, Baghdad, Iraq

<sup>5</sup> Department of Medical Laboratories Technology, Mazaya University College, Iraq

<sup>6</sup> Department of Medical Laboratories Technology, College of Pharmacy, National University of Science and Technology, Dhi Qar, Iraq

<sup>7</sup> Department of Medical Laboratories Technology, AL-Nisour University College, Baghdad, Iraq

## ARTICLE INFO

### Article history

Received: 27 December 2023

Revised: 30 January 2024

Accepted: 26 February 2024

Manuscript ID: [AJCA-2401-1483](#)

Checked for Plagiarism: **Yes**

Language Editor Checked: **Yes**

DOI: [10.48309/AJCA.2024.437914.1483](#)

### KEYWORDS

Photocatalytic degradation

Regeneration

Zinc oxide

Drug

Tetracycline

## ABSTRACT


In recent years, there has been an increase in the consumption of pharmaceuticals, especially antibiotics. Tetracycline (TC) is one of the widely used antibiotics, as it causes resistance to all microorganisms in ecosystems. In addition, it is classified as a controlled antibiotic. In this work, the efficiency of TC drug degradation via photolysis and hetero-generous photo catalytic methods is studied under effect of several volumes of H<sub>2</sub>O<sub>2</sub> (0-4 mL) as an oxidizing agent. Characterization of the sample was carried out via UV-visible spectroscopy, XRD, FESEM, EDX, and TEM. The reveal results the photocatalytic degradation of TC drug is 92.67 %, at the best conditions weight of catalyst ZnO NPs 0.3 g, volume of hydrogen peroxide (3 mL), and concentration of TC drug 50 mg/L, pH=6, at irradiation time 60 min. H<sub>2</sub>O<sub>2</sub> doses (0 and 4 mL) appear to have important variances in the first 10 min of the reaction for 4 mL of H<sub>2</sub>O<sub>2</sub> comparative with the solution without H<sub>2</sub>O<sub>2</sub> giving the best PDE% (98.44%). The (PDE%) rises as concentration of TC drugs decreases from (92.67%-29.76%), but light intensity increases. Regeneration/recycling of ZnO NPs the photo catalytic degradation efficiency was 88.9 %, 82.8 %, and 77.5% through 4 cycles compared to standard solution(fresh) was 92.67 %.

\* Corresponding author: Omran, Alaa A.

✉ E-mail: [aishamohaisha7@gmail.com](mailto:aishamohaisha7@gmail.com)

© 2024 by SPC (Sami Publishing Company)

## GRAPHICAL ABSTRACT

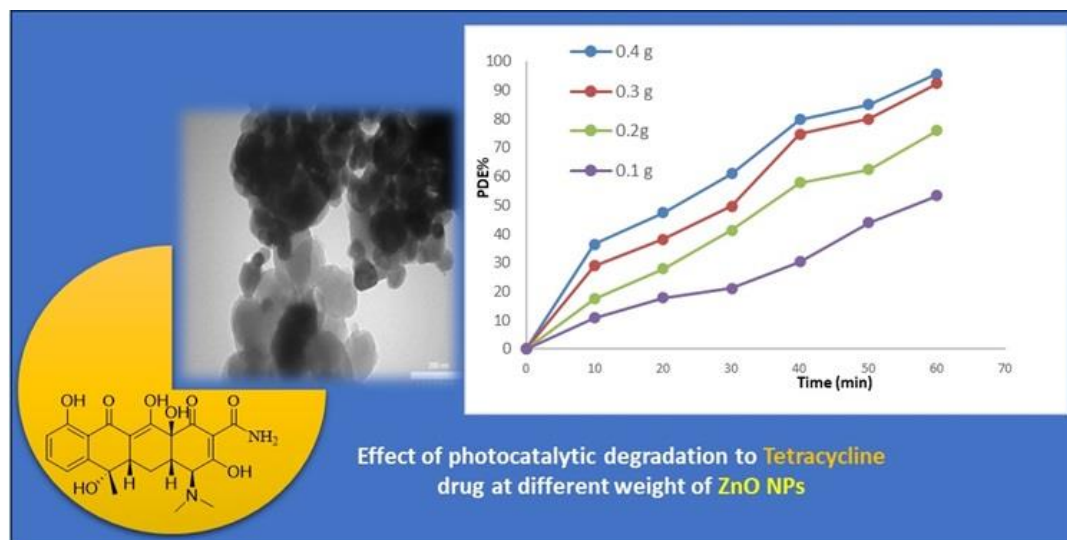

## Introduction

The term "advanced oxidation processes" (AOPs) describes a group of chemical treatment techniques used to oxidize organic (and occasionally inorganic) compounds in water and wastewater. These reactions take place in the presence of hydroxyl radicals. These oxidation techniques may effectively eliminate all contaminants, even those with minimal reactivity, and mineralize them thoroughly. Heterogeneous photocatalytic is one of the advanced oxidation processes used for removal of pharmaceutical and organic pollutant, in this type, the reactant and semiconductor will be found in different phase [1,2].

The photo catalysis is a process in which semiconductor absorbs light energy to form radicals in the solution, these radicals are capable of oxidizing or reducing destroying the target contaminants. Zinc oxide (ZnO) is a wide band gap ( $E_g = 3.37$  eV at room temperature, near-UV spectral region) semiconductor with high exaction binding energy (60 meV) enabling persistence of excitonic emission processes at or above room temperature. It has great potential for various applications, such as UV light

emitters, photo catalysts, surface acoustic wave devices, piezoelectric transducers, and optical waveguides [3-7]. Pharmaceutical are found in different types of water, for example wastewater, groundwater, surface water, and drinking water[8]. Pharmaceutical preparations are present in very small concentrations and quantities, causing various problems for living organisms. Aquatic organisms, such as fish, are affected by these pollutants, which it generates changes such as feminization or masculinization resulting from hormones and the environment, and it is difficult to get rid of them [9-11]. Since both birds and fish are important mediators in the food chain, the ingestion of these organisms affected by these pollutants leads to the accumulation of these pollutants in humans, and causes resistance to antibiotics, and tissue disorders [5,12-13].

Pathogenicity, a serious endocrine problem, and also serious problems for newborns. Antibiotics are now utilized in several settings counting livestock operations and aquaculture for therapeutic and treatment purposes [14-17]. Traces of antibiotics are created in several natural environments like aquatic ecosystems. Of these, those belonging to the family of antibiotics

$\beta$ -lactam are the ones that look utmost frequently, like cephalosporin, penicillin G, amoxicillin, and tetracycline which found in several concentrations ng/L to mg/L, both in surface waters and in waste water [18].

Tetracycline, have different brand names, and named as a four ("tetra-") hydrocarbon rings ("-cycl-") derivation ("-ine"). is an antibiotic in the tetracycline's family of drugs, utilized to treat a number of infections, like plague, cholera, acne, brucellosis, malaria, and syphilis. Its chemical formula is  $C_{22}H_{24}N_2O_8$ , Molar mass is  $444.440 \text{ g.mol}^{-1}$ , and chemical structure of a drug is shown in Figure 1 including side effects have diarrhea, poor tooth, sun burning, vomiting, kidney problems rash, and loss of appetite [19-22].

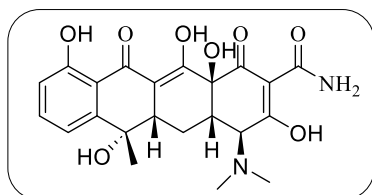


Figure 1. Chemical structure of tetracycline drug.

## Experimental Part

### Materials

The zinc acetate, Oxalic acid, and hydrogen peroxide were purchased via supported from (Sigma-Aldrich, Germany). Tetracycline TC drug was purchased from factory samara-Iraq. All chemicals used in the research that degree analytical and used directly without purification.

### Preparation of ZnO NPs

Hydrothermal process was utilized to prepare ZnO NPs. Initially, in a beaker dissolving zinc acetate 5 g in 50 mL distilled water, and dissolving Oxalic acid in 8g in 50 mL distilled water, and then mixing two beakers to formation of a ZnO colloid. The solution was transferred in Teflon cup (the autoclave) in an oven at to  $140^\circ\text{C}$

for 24 hours, as explained in details for another groups [23].

### Photocatalytic experiment

The photo degradation of TC drug as a pharmaceutical pollutant model was studied by means of photocatalysts. 200 mL solution TC drug with a 50 mg/L concentration with photocatalyst was stirred for 10 min in the dark (adsorption) with 0.3 g of ZnO NPs. The solution was irradiated via (UVA-meter) with  $1.21 \text{ mw/cm}^2$  as visible light sources for 60 min, and sampled every 10 min. During the photocatalytic degradation, at  $25^\circ\text{C}$ . The absorbance of TC drug solution was recorded by a spectrophotometer ( $\lambda_{\text{max}} = 335 \text{ nm}$ ), and photocatalytic degradation efficiency (%PDE) of drug was obtained using Equation (1):

$$\text{PDE (\%)} = (C_0 - C_t) / C_0 \times 100 \quad (1)$$


## Result and discussion

### Characterization

The surface morphology of the synthesized nanomaterials can be examined via employing SEM analysis. The morphology of the nanoparticles differs from small spherical particles to big polyhedral nanoparticles. According to the image SEM, ZnO NPs had spherical-like morphology with some agglomeration in cluster form. From image SEM it can be noticed that the particle sizes are clearly. The scanning electron microscopy is an ideal analytical technique for characterizing and visualizing the elemental composition of a specimen [5,24]. The transmission electron microscopy gives a more accurate picture of the structure of prepared samples; the crystalline, distribution and the particles size of nanoparticle, as shown in Figure 2a.

The TEM image clearly shows that the ZnO NPs consist of spherical and hexagonal like shapes and mostly with particle sizes smaller than 200


nm. In addition, the TEM images show significant agglomerations of nanoparticles which may be due to the annealing of the sample at an almost high temperature. It is reported previously that the surface energy and specific surface area of nanoparticles are significantly higher than those of larger particles. Hence, the nanoparticles tend to agglomerate in liquid media at high temperature [5, 25-26], as depicted in Figure 2b.

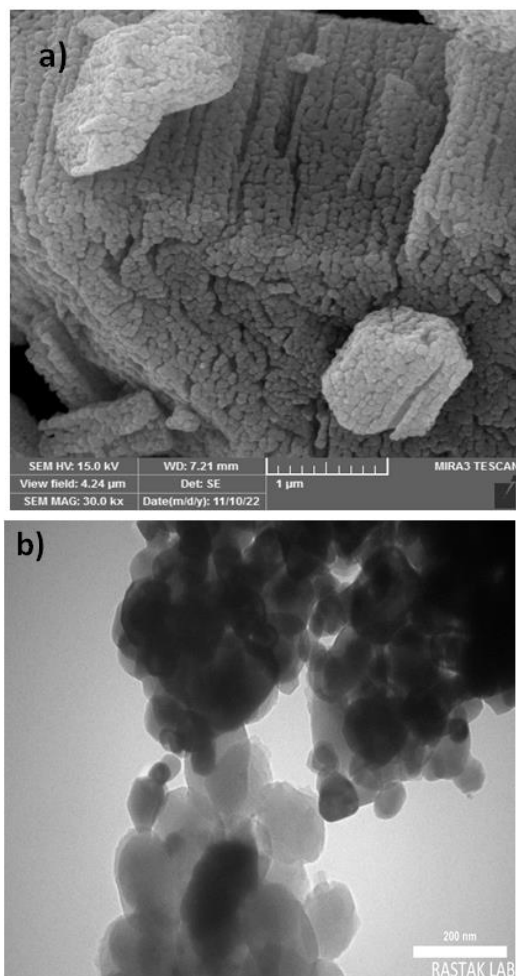

**Figure 2.** Effect of a) SEM of ZnO NPs and b) TEM of ZnO NPs.


X-ray diffraction is a highly effective non-destructive way for crystalline material characterization. Figure 3 shows the XRD patterns of pure ZnO NPs. The calcined ZnO NPs at 500 °C XRD patterns. After calcination at 500 °C, impurities are removed and crystallinity is improved. At 500 °C, all ZnO NPs peaks were

discovered to be sharper, confirming that crystal formation occurs at higher calcination temperatures. The existence of ZnO NPs crystalline peaks at (31.6°, 34.4°, 36.2°, 47.4°, 56.6°, 62.8°, 67.8°, and 69°). All the diffraction peaks can also be well indicating to the hexagonal Wurtzite structure of ZnO NPs. Pure phase with highly crystalline was produced due to very sharp and intense peaks [27,28].

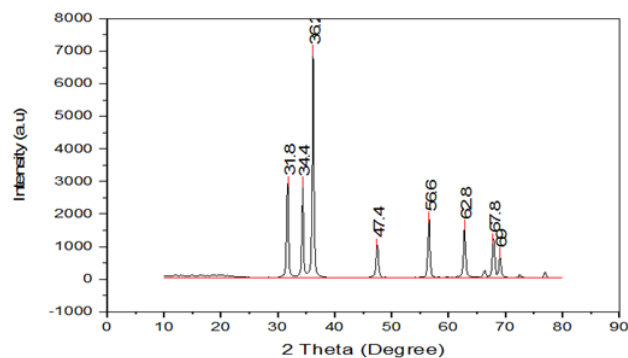

**Figure 3.** X-ray diffraction of ZnO NPs.


Energy dispersive spectroscopy EDX verified the ZnO NPs existence. Strong and precise diffraction peaks show that the nanocrystal line ZnO NPs good crystallinities EDX spectra show that only Zn, C, and O can be found in pure ZnO NPs A semi-quantitative evaluation of the atomic concentration (atom%) is demonstrated in Figure 4 which shows that the products' Zinc (Zn), Oxygen (O) and, Carbon (C) elements content (70.5 %, 25.0%, and 4.5 %), respectively [28].

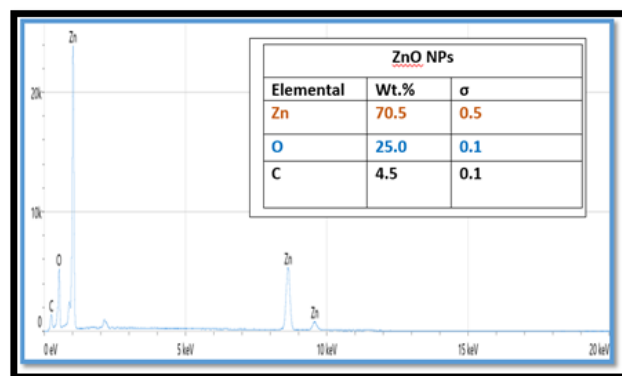

**Figure 4.** Energy dispersive spectroscopy EDX of ZnO NPs.

### Effect of weight ZnO NPs


The impact of the weight of ZnO NPs (0.1-0.4 g) on the photocatalytic degradation of TC drug was investigated at 25 °C, 50 mg/L, flow rate of O<sub>2</sub> (5 mL/min) light intensity (1.2 mW/cm<sup>2</sup>), and solution pH 6.1 when the weight of ZnO NPs increase the photocatalytic degradation increase because the number of active sites increase, as illustrated in Figure 5. This shows that the present degradation of modified catalyst increase with increase in the amount of catalyst from 0.1-0.3 g/L and photocatalytic degradation increase (53.77% to 92.99 %) but above this limit is few changes or retained without notice change of photocatalytic degradation. This indicate that the active site provided for the adsorption of substrate on the catalyst surface is limited to catalyst amount of 0.3 g/L and after that low change in the degradation [17,29].

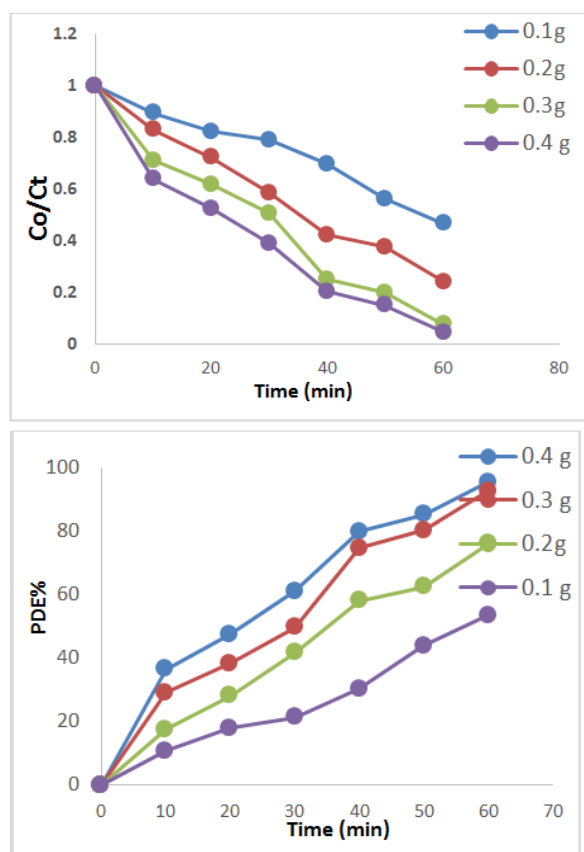

**Figure 5.** Effect of photocatalytic degradation to TC drug at different weight of ZnO NPs.

### Effect of concentration of TC drug

The effect of initial concentration of TC drug (25-100 mg/L) on photocatalytic degradation method of TC drug was studied utilizing 0.3 g/L. The light intensity (1.2 mW/cm<sup>2</sup>) at 25 °C. It has been observed that of photo catalytic degradation gradually decreases with increasing of initial concentration of TC drug, this behavior could be explained the concentration 50 mg/L was the optimum concentration to over largest area of the ZnO NPs. Therefore, the photocatalytic degradation was decreased, but the TC drug concentration 50 mg/L gives the best optimum photo catalytic degradation efficiency which is 92.99 %, as shown in Figure 6 [30,31].

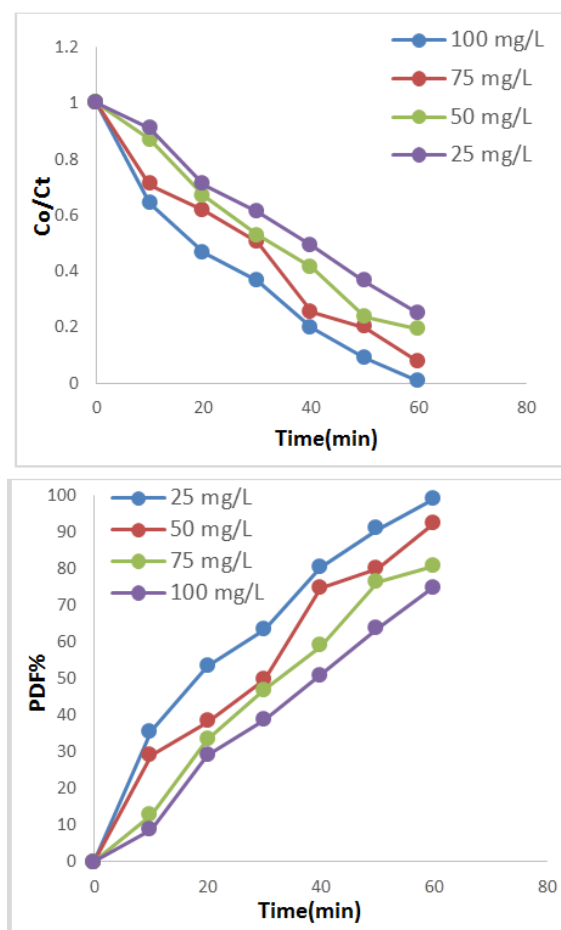


**Figure 6.** Effect of photocatalytic degradation to TC drug at different concentrations of TC drug.



### Roles of reactive oxygen species (ROS)


To distinguish the contribution of the surface reaction with ( $\text{OH}^\bullet$ ,  $\text{O}_2^{\cdot-}$ , and  $\text{H}_2\text{O}_2$ ) species, several ROS were employed for check their impact on the relative photonic efficiencies of TC drug. The reaction pathway of drug degradation through generation of radicals from photo generated electron-hole pairs ( $e^-_{\text{CB}}$ ;  $h^+_{\text{VB}}$ ). Hydroxyl radicals and electrons and holes ( $e^-_{\text{CB}}$ ;  $h^+_{\text{VB}}$ ) have an affected on photo catalytic degradation process.  $\text{OH}^\bullet$  radical considered oxidizing agent which contributing to photo catalytic degradation of organic substrate. Nevertheless  $e^-$  can be recombination with  $h^+$  causing decrease in the availability of the photo induced  $h^+$  without electron acceptor, the limitation lead to the recombination of electrons and holes reduce photo catalytic efficiency and cause radiation energy loss, therefore suppressing the recombination of electrons and holes is an important in enhancing the performance of photo catalytic degradation [32], while when methanol was added, the photo catalytic degradation changed and reduced indicating that  $\text{OH}^\bullet$  can be important in the photo catalytic, and shows that degradation efficiency between  $\text{H}_2\text{O}_2$  and Methanol, as demonstrated in Figure 7.

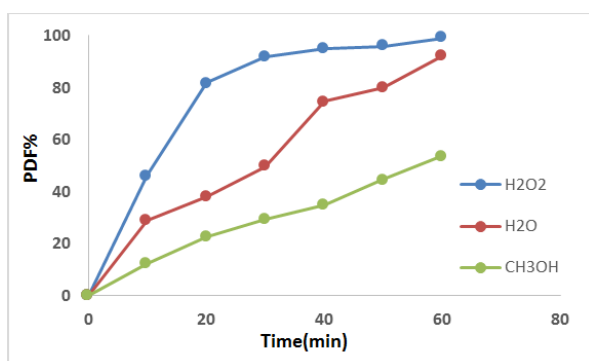

**Figure 7.** Effect  $\text{H}_2\text{O}_2$  on photocatalytic. Experimental conditions: 0.3 g, TC drug concentration 50 mg/L, and light intensity  $1.2 \text{ mW/cm}^2$ .

Effect of several doses of  $\text{H}_2\text{O}_2$  (0 and 4 mL) as an oxidizing agent. The reveal results the

photocatalytic degradation of TC drug is 92.9 %, at the best conditions weight of catalyst ZnO NPs 0.3 g, volume of  $\text{H}_2\text{O}_2$  (3 mL), and concentration of TC drug 50 mg/L, pH=6, at irradiation time 60 min. The  $\text{H}_2\text{O}_2$  doses (0 and 4 mL) appear important variances in the first 10 min of the reaction for 4 mL of  $\text{H}_2\text{O}_2$  comparative with the solution without  $\text{H}_2\text{O}_2$  gave the best PDE% (99%), as shown in Figure 8 [2,29].

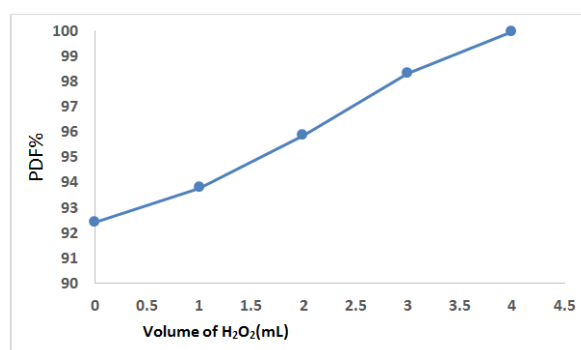


**Figure 8.** Effect of volume hydrogen peroxide.

### Regeneration /Recycling of ZnO NPs

To reduce the economic cost using an environmentally friendly surface that is easily prepared from available, inexpensive materials, it can be used more than once to remove pollutants because of the surface's high efficiency and active sites that can be reactivated. The ZnO NPs regeneration is one of the important steps in assessing the practical useful of photo catalysts and in developing heterogeneous photo activity technology for waste water treatment.

An examination of the photo catalytic activity of the reused of ZnO NPs was carried out onto TC drug. The photo catalytic degradation efficiency were 88.9%, 82.8 %, and 77.5% three cycle compared to standard solution (fresh (1)) was 92.9%, as shown in Figure 9. The result of photo catalysts is effective, and thus the photo catalyst is basically stable and is therefore promising for environmental remediation [33,34].

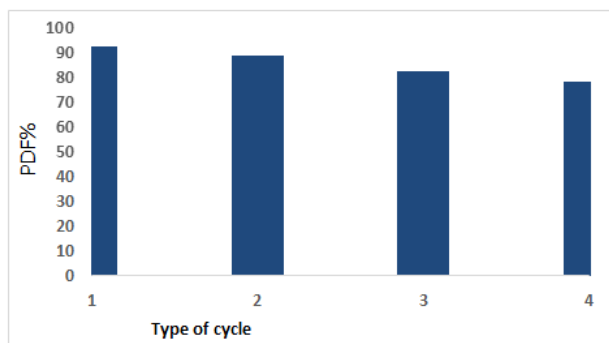

**Figure 9.** Effect of regeneration/recycling of ZnO NPs.

## Conclusion

The aim of the study was to evaluate the efficiency of a catalyst ZnO NPs by assisted photocatalytic method by TC drug, an antibiotic major utilized in veterinary human and medicine. Initially, Photocatalytic degradation of TC drugs necessary to degrade 50 mg /L of TC drug, and 60 min. Thus, it is sufficient to fully degrade 50 mg/L drug and 92.9 % from aqueous solution. The TC drug was completely degraded after 1 hr of illumination; the good removal was obtained at 0.3 g. More than 98% of TC drugs have been oxidized after 1 hour irradiation time at the best condition of photocatalytic degradation. The good reactive oxygen species (ROS) were found when utilized ( $H_2O_2$ ) comparative with methanol. Thus, the  $H_2O_2$  is significant in improving the performance of photocatalytic degradation.


## Disclosure statement


No potential conflict of interest was reported by the authors in this study.

## Orcid

Rafid Tajaldeen : [0000-0002-6591-2073](https://orcid.org/0000-0002-6591-2073)

Mohammed B. Alqaraguly : [0000-0003-0083-7436](https://orcid.org/0000-0003-0083-7436)

Ola Hamad Salah : [0000-0002-3194-1749](https://orcid.org/0000-0002-3194-1749)

Zahraa Hamzaa Abud Alzahraa : [0000-0003-2809-5884](https://orcid.org/0000-0003-2809-5884)

Alaa A. Omran : [0000-0002-5688-447X](https://orcid.org/0000-0002-5688-447X)

## References

- [1] N.A. Hussain, A. Taifi, O.K.A. Alkadir, N.H. Obaid, Z.M. Abboud, A.M. Aljeboree, A.L. Al Bayaa, S.A. Abed, A.F. Alkaim, Role of Pomegranate peels as a activated carbon for removal of pollutants, *IOP Conference Series: Earth and Environmental Science*, IOP Publishing, **2022**, 012028. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [2] A. Mishra, A. Mehta, S. Kainth, S. Basu, A comparative study on the effect of different precursors for synthesis and efficient photocatalytic activity of gC 3 N 4/TiO 2/bentonite nanocomposites, *Journal of Materials Science*, **2018**, 53, 13126-13142. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [3] R. Nithya, S. Ragupathy, D. Sakthi, V. Arun, N. Kannadasan, Photocatalytic efficiency of brilliant green dye on ZnO loaded on cotton stalk activated carbon, *Materials Research Express*, **2020**, 7, 075002. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [4] N. Matinise, X. Fuku, K. Kaviyarasu, N. Mayedwa, M. Maaza, ZnO nanoparticles via Moringa oleifera green synthesis: Physical properties & mechanism of formation, *Applied Surface Science*, **2017**, 406, 339-347. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [5] J.P. Dhal, B.G. Mishra, G. Hota, Hydrothermal synthesis and enhanced photocatalytic activity of ternary Fe 2 O 3/ZnFe 2 O 4/ZnO nanocomposite through cascade electron transfer, *RSC Advances*, **2015**, 5, 58072-58083. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [6] A.M. Aljeboree, Z.D. Alhattab, U.S. Altimari, A.K.O. Aldulaim, A.K. Mahdi, A.F. Alkaim, Enhanced removal of amoxicillin and chlorophenol as a model of wastewater pollutants using hydrogel nanocomposite: Optimization, thermodynamic, and isotherm

- studies, *Caspian Journal of Environmental Sciences*, **2023**, 21, 411-422. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [7] Mohamed, M. Barakat, Enhancement of photocatalytic activity of ZnO/SiO<sub>2</sub> by nanosized Pt for photocatalytic degradation of phenol in wastewater, *International Journal of Photoenergy*, **2012**, 2012. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [8] I.A. Latif, H.M. Abdullah, S.H. Marza, A.H. Al-Dujaili, E.T. Bakir, Synthesis, Characterization and Electrical Properties of ZnO Nanoparticles Dispersed in Poly (vinyl acetal)/PVA Composite, *Asian Journal of Chemistry*, **2013**, 25, 7753-7757. [[Google Scholar](#)], [[Publisher](#)]
- [9] A. Ahmadpour, Investigation of Photocatalytic Degradation Process in Wastewater Treatment Industry. *Journal of Engineering in Industrial Research*, **2022**, 3, 189-202. [[CrossRef](#)], [[Publisher](#)]
- [10] T. Alemayehu, A. Sergawie, Determination of chloramphenicol in pharmaceutical samples at electrochemically pretreated glassy carbon electrode, *ASRJETS*, **2013**, 6, 1-11. [[Google Scholar](#)], [[Publisher](#)]
- [11] Z. Khedaer, D. Ahmed, S. Al-Jawad, Investigation of morphological, optical, and antibacterial properties of hybrid ZnO-MWCNT prepared by sol-gel, *Journal of Applied Sciences and Nanotechnology*, **2021**, 1, 66-77. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [12] Z.D. Alhattab, A.M. Aljeboree, M.A. Jawad, F.S. Sheri, A.K. Obaid Aldulaim, A.F. Alkaim, Highly adsorption of alginate/bentonite impregnated TiO<sub>2</sub> beads for wastewater treatment: Optimization, kinetics, and regeneration studies, *Caspian Journal of Environmental Sciences*, **2023**, 21, 657-664. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [13] A.M. Aljeboree, G.S. Hamid, A.A. Katham, M.M. Abdulkadhm, H.A. Lafta, A.M.B. Al-Dhalimy, A.F. Alkaim, S.A. Abed, Highly adsorbent surface from watermelon peels: as non-conventional low-cost sorbent; Equilibrium and Recycle study, *IOP Conference Series: Earth and Environmental Science*, *IOP Publishing*, **2022**, 012008. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [14] M. Ayoub, Degradation of tetracycline using nanoparticles of zero-valent iron and copper, *Water Practice & Technology*, **2022**, 17, 246-253. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [15] Malumi, S. O., Malumi, T., Osiele, M. O., Ekpeko, A., Ikhioya, I. L. Enhance and Performance Evolution of Silver-Doped Titanium Dioxide Dye-Sensitized Solar Cells Using Different Dyes. *Journal of Engineering in Industrial Research*, **2023**, 4, 189-200. [[CrossRef](#)], [[Publisher](#)]
- [16] Y. Liu, Y. Ohko, R. Zhang, Y. Yang, Z. Zhang, Degradation of malachite green on Pd/WO<sub>3</sub> photocatalysts under simulated solar light, *Journal of Hazardous Materials*, **2010**, 184, 386-391. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [17] H. Abbasi, F. Salimi, F. Golmohammadi, Removal of cadmium from aqueous solution by nano composites of bentonite/TiO<sub>2</sub> and bentonite/ZnO using photocatalysis adsorption process, *Silicon*, **2020**, 12, 2721-2731. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [18] S. Halder, R. Dammalapati, B. Bhaduri, ZnO nanoparticles dispersed in nitrogen-enriched carbon matrix for the efficient adsorption and photocatalytic degradation of aqueous methylene blue molecules, *Inorganic Chemistry Communications*, **2023**, 158, 111685. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [19] Y. Ma, N. Gao, C. Li, Degradation and pathway of tetracycline hydrochloride in aqueous solution by potassium ferrate, *Environmental Engineering Science*, **2012**, 29, 357-362. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [20] T.M.P. Nguyen, H.T. Van, M. Yilmaz, T.K. Hoang, Q.T. Nguyen, T.M.H. Vi, L.T.Q. Nga,



- Removal of Tetracycline from aqueous solution using composite adsorbent of ZnAl layered double hydroxide and bagasse biochar, *Environmental Technology & Innovation*, **2022**, 28, 102914. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [21] J. Jeong, W. Song, W.J. Cooper, J. Jung, J. Greaves, Degradation of tetracycline antibiotics: mechanisms and kinetic studies for advanced oxidation/reduction processes, *Chemosphere*, **2010**, 78, 533-540. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [22] F. Ahmad, D. Zhu, J. Sun, Environmental fate of tetracycline antibiotics: degradation pathway mechanisms, challenges, and perspectives, *Environmental Sciences Europe*, **2021**, 33, 64. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [23] M. Adel, M.M. Kadhim, H.H. Muttashar, S.K. Hachim, S.A. Abdullaha, A.M. Rheima, Two-dimensional silicon carbide monolayer as a promising drug delivery vehicle for hydroxyurea anti-cancer drug, *Korean Journal of Chemical Engineering*, **2023**, 40, 1433-1439. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [24] Y. Sun, L. Chen, Y. Bao, Y. Zhang, J. Wang, M. Fu, J. Wu, D. Ye, The applications of morphology controlled ZnO in catalysis, *Catalysts*, **2016**, 6, 188. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [25] A. Dang, Z. Yuan, X. Liu, S. Ma, Y. Yang, A. Zada, Y. Gao, Y. Liu, T. Li, Y. Han, Graphene oxide mediated carbon foam/CNTs composites for highly efficient adsorption of methylene blue and mechanism insight, *Ceramics International*, **2023**, 49, 36970-36978. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [26] M. Irani, T. Mohammadi, S. Mohebbi, Photocatalytic degradation of methylene blue with ZnO nanoparticles; a joint experimental and theoretical study, *Journal of the Mexican Chemical Society*, **2016**, 60, 218-225. [[Google Scholar](#)], [[Publisher](#)]
- [27] M.B. Babu, K. Madhuri, Synthesis and electrochromic properties of nanocrystalline WO<sub>3</sub> thin films, *Physica B: Condensed Matter*, **2020**, 584, 412068. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [28] F.H. Abdulrazzak, R.B. Jimaa, I.M. Radhi, T.A. Himdan, XRD and Microscopic Images for Synthesis Graphite Nanoparticles by Oxidation Method, *NeuroQuantology*, **2021**, 19, 45. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [29] S.S. Sambaza, A. Maity, K. Pillay, Polyaniline-coated TiO<sub>2</sub> nanorods for photocatalytic degradation of bisphenol A in water, *ACS omega*, **2020**, 5, 29642-29656. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [30] M. Saeed, M. Muneer, M.K.K. Khosa, N. Akram, S. Khalid, M. Adeel, A. Nisar, S. Sherazi, Azadirachta indica leaves extract assisted green synthesis of Ag-TiO<sub>2</sub> for degradation of Methylene blue and Rhodamine B dyes in aqueous medium, *Green Processing and Synthesis*, **2019**, 8, 659-666. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [31] J. Kaur, S. Singhal, Heterogeneous photocatalytic degradation of rose bengal: effect of operational parameters, *Physica B: Condensed Matter*, **2014**, 450, 49-53. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [32] D.H. Tseng, L.C. Juang, H.H. Huang, Effect of oxygen and hydrogen peroxide on the photocatalytic degradation of monochlorobenzene in aqueous suspension, *International Journal of Photoenergy*, **2012**, 2012. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [33] S.L. Wong, M.H. Mohamed Noor, N. Ngadi, I. Mohammed Inuwa, R. Mat, N.A. Saidina Amin, Aspirin adsorption onto activated carbon derived from spent tea leaves: statistical optimization and regeneration study, *International Journal of Environmental Research*, **2021**, 15, 413-426. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]

- [34] K. Sivaranjani, S. Sivakumar, J. Dharmaraja, Enhancement photocatalytic activity of Mn doped CdS/ZnO nanocomposites for the degradation of methylene blue under solar light irradiation, *Advances in Materials Science*, **2022**, 22, 28-48. [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]

#### HOW TO CITE THIS ARTICLE

Rafid Tajaldeen, Mohammed B. Alqaraguly, Ola Hamad Salah, Alzahraa S. Abdulwahid, Talib Munshid Hanoon, Zahraa Hamzaa Abud Alzahraa, Alaa A. Omran. Enhanced Photocatalytic Performance of ZnO NPs in the Presence of Solar Light and H<sub>2</sub>O<sub>2</sub> for Degradation of Tetracycline from Wastewater: Optimal Conditions for Green Products. *Adv. J. Chem. A*, 2024, 7(4), 396-405.

DOI: [10.48309/AJCA.2024.437914.1483](https://doi.org/10.48309/AJCA.2024.437914.1483)

URL: [https://www.ajchem-a.com/article\\_191348.html](https://www.ajchem-a.com/article_191348.html)